



# Experimental Investigation of Recycled Alkali Activated Slag in Plain and Reinforced Concrete

Jonnalagadda Rakesh<sup>1</sup>, Mohammed Ismail<sup>2</sup>  
M.Tech Student<sup>1</sup>, Assistant Professor<sup>2</sup>  
Department of Civil Engineering  
Pydah College of Engineering and Technology, India

## Abstract:

The production of OPC is responsible for about 7% of the world's CO<sub>2</sub> emission, a major contributor to the greenhouse effect which is implicated in global warming and climatic changes, lead to the search for more environmentally viable alternative to cement. One of those alternative material is alkali activated slag where ground granulated blast furnace slag is used not as partial replacement to cement but also as a sole binder in the production of concrete. The performance of alkali-activated slag concrete with sodium silicate, sodium hydroxide, sodium carbonate as activator are used at 4% Na<sub>2</sub>O and 4% of hydrated lime by total weight of solid binder content if used as a retarder. The scope of the work covered four mixes: - Normal OPC mix and three alkali activated slag mixes of the same binder content and the same water binder ratio. The fresh concrete properties studied were setting time and workability and the Engineering properties studied are compressive strength was measured in 1,7,28 days, split tensile strength was measured in 7,28 days and flexure, punching shear strength was compared in 12 days only. The AAS concrete with different activators investigated was found to achieve good workability comparable with that of OPC. Sodium silicate, sodium hydroxide activated slag mixes sets very quickly. Among AAS mix sodium silicate was the best; sodium carbonate was the second; and sodium hydroxide was third in terms of compressive, split tensile strengths and in terms of flexure strength and punching shear strength sodium hydroxide was best; sodium carbonate was second; sodium silicate was third.

**Keywords:** Alkali Activated Slag Concrete, Ground Granulated Blast Furnace Slag, OPC, Compressive Strength, Split Tensile Strength.

## I. INTRODUCTION

Portland cement clinker is made from calcinations of limestone and siliceous material where de-carbonation occurs according to reaction:



The total emission of CO<sub>2</sub> per kg of cement clinker produced is 0.53 kg from the decarburization of calcite, plus 0.33 kg from the burning process plus 0.12kg from the generation of electrical power required, making a total of 0.98kg. Therefore, for every ton of cement clinker produced, an approximately equal amount of carbon dioxide is released into Atmosphere (Davidovits, 1991). The world cement industry Contributes some 7% to the total man made CO<sub>2</sub> emission. This leads to the search for more environmentally viable alternatives to Portland cement. One of these alternative materials is alkali-activated slag, in which ground granulated blast-furnace slag is used not as a partial replacement for cement but as a sole binder itself in the production of concrete. This will produce an environmentally friendly concrete. The use of slag cement has advantages due to its excellent cementations properties over Ordinary Portland cement. Various studies had investigated ways to enhance the reactivity of the slag. One of the economic ways of activation is alkali activation. The alkalis that are going to be used in this dissertation are (Na<sub>2</sub>SiO<sub>3</sub>), (Na<sub>2</sub>CO<sub>3</sub>) and (NaOH). There are many slag like granulated blast-furnace slag, electro thermal furnace phosphorous slag and steel slag but GGBS is generally used. Slag has latent hydraulic properties. If GGBS is placed in water alone, it dissolves to a small extent but a protective film deficient in Ca<sup>2+</sup> is quickly formed, which inhibits further

reaction. Alkali activated slag is not a widely known and used construction material. Most of the research has been done at the material development stage dealing with paste and mortar specimens to study the material chemistry and microstructure. The scope of the work covers a normal strength OPC control mix, AAS mixes with the same binder content and the same w/b ratio. The AAS concrete comprise three mixes with slag as the sole binder activated with three alkalis sodium silicate, sodium carbonate and sodium hydroxide with a dosage of 4% Na<sub>2</sub>O. The normal water curing was used.

## II. MATERIALS

### Cement

Ordinary Portland cement, conforming to the requirements of – IS 12269: 1987 was used in this investigation. The following Chemical properties are produced by the manufacturer.

**Table.1. Chemical properties of cement**

Description	In%
SiO <sub>2</sub>	21.3
Al <sub>2</sub> O <sub>3</sub>	4.5
Fe <sub>2</sub> O <sub>3</sub>	4.0
MgO	2.4
CaO	63.1
Na <sub>2</sub> O	0.1
K <sub>2</sub> O	1.2
SO <sub>3</sub>	2.2

### Slag

The Ground Granulated Blast-Furnace Slag (GGBS) used was obtained from the Toshali Cements pvt. Ltd., It complied with

BS: 6699-1992 and the Chemical properties are produced by the manufacturer.

**Table.2. Chemical properties of slag**

Description	In%
Magnesium Oxide	8.29
Sulphur Content	0.29
Sulphide Sulphur	0.54
Loss on Ignition	NIL
Insoluble Residue	0.46
Chloride	0.014
Moisture Content	0.48
Manganese content	0.26
Glass content	94.00
Finess(m <sup>2</sup> /kg)	360
Soundness	NIL

**Sodium Silicate Powder**

Powder form of sodium silicate was used in the investigation. It has a molecular ratio SiO<sub>2</sub>: Na<sub>2</sub>O =3.21 with 29.2% of SiO<sub>2</sub> and 9.1% of Na<sub>2</sub>O by weight.

**Sodium Carbonate**

Sodium carbonate powder. It is almost 99.5 % pure. The powder is used to make solution of required dosage in water.

**Sodium Hydroxide Pellets**

Sodium hydroxide pellets. It is 97 % pure. The pellets are used to make solution of required dosage in water.

**III. MIX DESIGN**

The notation for the mixes is as follows

**CM:** Ordinary Portland cement (OPC) control mix with w/c=0.43.

**SS4:** Sodium silicate powder -activated slag concrete mixture with Na<sub>2</sub>O content of 4% by weight of slag with w/c=0.43.

**SH4:** Sodium hydroxide-activated slag concrete mixture with Na<sub>2</sub>O content of 4% by weight of slag with w/c=0.43.

**SC4:** Sodium carbonate-activated slag concrete mixture with Na<sub>2</sub>O content of 4% by weight of slag and with w/c=0.4

**WORKABILITY**

The workability of concrete describes the homogeneity and the ease of mixing, handling, placing, compacting and finishing of the concrete (or mortar). Workability or rheology of fresh concrete is the term traditionally been used in concrete technology to embrace all the necessary qualities. The test used is slump test.

**A. Result and Discussion**

The results from above Table show acceptably workable concrete with the CM, having the lower slump than AAS concrete which has same w/c ratio. From the results displayed in above Table it can be concluded that the workability of sodium silicate activated slag concrete at Ms=1 when there is no addition of lime has high workability when compared with the addition of lime slurry mixed water glass activated slag concrete, which is in agreement with the results published by Shi et al., (2006) where they also found the workability of sodium silicate activated slag concrete is very high when the modulus is between

0.5 and 1.0. For the same modulus of sodium silicate and at the same dosage, but with the addition of 4% lime by weight of slag resulted in loss of workability from collapse to 145 mm in terms of slump, which shows that due to the addition of lime slurry there exists loss of workability. This finding is in agreement with the work done by Chen and Liao, 1992. The sodium carbonate activated slag also shows high workability when compared to the control mixes. Among AAS concrete, sodium hydroxide activated slag concrete with the addition of hydrated lime has lower workability but is comparable with the workability of control mixes

**Table.3. the slump at 5 minutes**

Activator	Slump(mm)
CM	135
SS4	145
SH4	110
SC4	125

**Test procedure**

The test was carried out in accordance to IS4031 (part 5)1988 using the vicat's apparatus. The apparatus consists of steel needle which acts under a prescribed weight of 300 ± 1 g to penetrate the mortar. The penetration was repeated for every 10 min and during the interval the sample was kept in a chamber under a controlled temperature (20 ± 2) °C and 90% relative humidity. Two different needles were used to determine the initial and final setting. The initial set needle was a right cylinder of diameter 1.13 ± 0.05 mm. The initial setting time was recorded when the sample is sufficiently stiff so that the needle penetrates no deeper than 4 ± 1 mm from the bottom. The final set needle is a similar needle with an attachment that helps to identify when it penetrates the mortar to a depth of only 0.5 mm. The setting values are related to many variables such as cement composition and temperature and the typical data on setting of different types of cement are shown in Table below.

**Table.4. Setting time of mixes**

Cement Type	Initial Setting(h:min)	Final Setting(h:min)
OPC (CM)	0:30	3:10
SS4	0:20	0:50
SH4	0:10	0:30
SC4	1:0	2:15

**B. Result and Discussion**

Among the mixes of the same w/c ratio and binder content the addition of slag prolongs the setting time. The sodium silicate activated slag mortar with modulus of silica (Ms=1) and 4 % Na<sub>2</sub>O dosage has shorter setting time of all the mixes and Na<sub>2</sub>CO<sub>3</sub> activated slag mortar exhibited longer setting times (Initial and Final) among AAS mortar mixes. From the above table it is evident that the addition of 4% hydrated lime by weight of slag prolongs the final setting time of sodium silicate activated slag by 50 minutes.

**IV.ENGINEERING PROPERTIES**

The Engineering properties of concrete including the Compressive Strength, Split Tensile Strength, Flexural Strength and Punching Shear of different concrete mixes OPC and three AAS mixes with different activators. The influence of curing conditions at different ages is presented.


**A. Compressive Strength Test**

Compressive Strength is an important criterion used to evaluate the quality of concrete. The Compressive Strength is done as

determined in IS456:2000 and two samples were tested at 1, 7 and 28 days, and the average results are reported.

**Table.5. Compressive strength at different ages**

Cement or Slag mix	1- Day Strength(Mpa)	7-Day Strength(Mpa)	28-Day Strength(Mpa)
CM	9.5	25.08	38.10
SS4	12.46	22.87	31.09
SH4	12.04	23.66	27.32
SC4	05.73	20.03	29.15

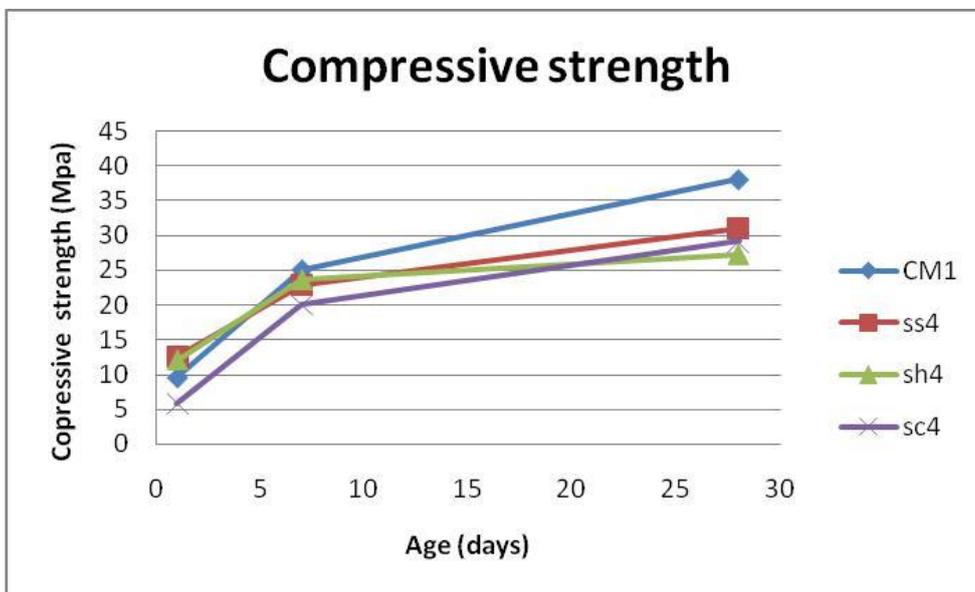

**Figure.1. Compressive Strength Result in Graphical Representation**

**B. Result on Compressive Strength**

It can be seen in Fig.1 that Na<sub>2</sub>SiO<sub>3</sub>(SS4) with a dosage of 4% Na<sub>2</sub>O by weight of slag achieved higher compressive strength (31.09 MPa at 28 days respectively in water curing) in comparison with all the other mixes. Na<sub>2</sub>CO<sub>3</sub>(SC4) activated concrete exhibited second highest compressive strength (29.15 MPa at 28 days) among alkali-activated concrete mixes.


NaOH(SH4) activated slag concrete mix has compressive strength 27.32 Mpa at 28 days.

**C. Split Tensile Strength Test**

The Splitting Tensile Test is a simple test to perform and it is believed that it leads to a close value of direct tensile strength. The test was performed as described in IS 5816: 1999 and three samples were tested at the ages 7 and 28 days for water curing and average values are reported.

**Table.6. Split tensile strength at different ages**

Cement or Slag mix	7-Day Strength(Mpa)	28-Day Strength(Mpa)
CM	2.31	2.8
SS4	1.87	2.59
SH4	1.79	2.16
SC4	1.83	2.47

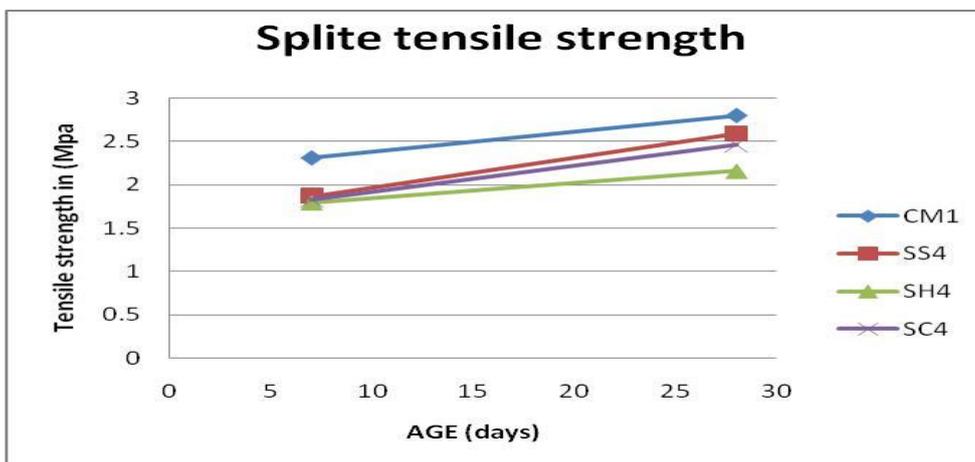

**Figure. 2. Split Tensile Strength Result in Graphical Representation**

#### D. Result on Split Tensile Strength


The results in above table show that among AAS concrete mixes, SS4 showed the highest value of tensile strength around 2.59 MPa at 28 days followed by SC4 (2.47 MPa). SH4 showed the lowest value (2.16 MPa).

#### E. Flexural Strength Test

The Flexural Strength of concrete mixes was measured according to I.S.9399:1979. Samples of 150x150x700 mm were cast in order to perform the Flexural Strength Test and two samples were tested for curing at the age of 12 day and average are reported.

**Table.7. Flexure strength at 12 day age**

Cement or Slag mix	12-Day Strength(Mpa)
CM	1.87
SS4	0.89
SH4	1.18
SC4	1.13

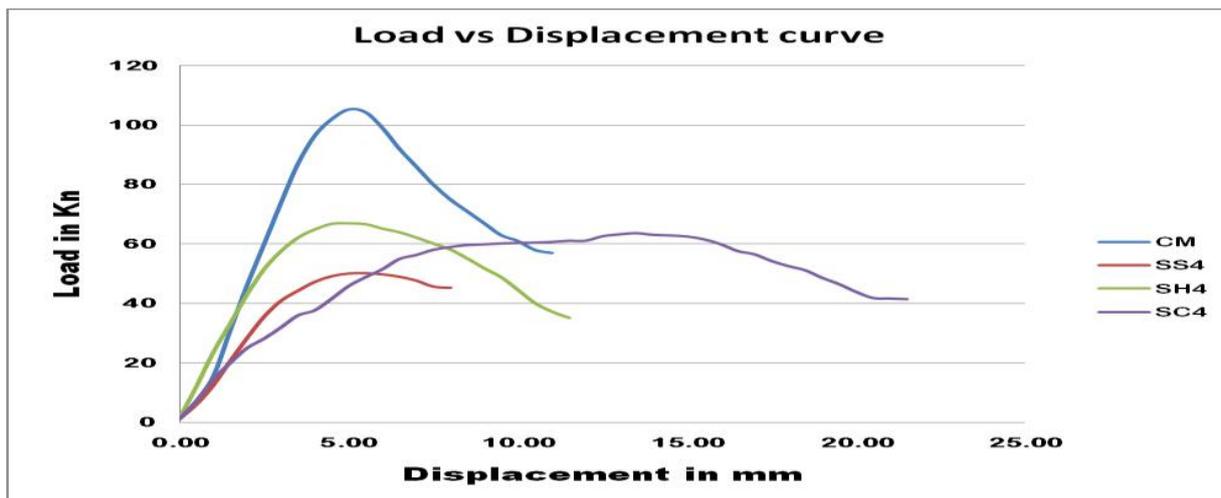

**Figure. 4. Load Vs Displacement of Flexure Strength**


#### F. Results on Flexural Strength

From the above figure we can observe effect of curing on all different mixes. The highest flexural strength is shown by concrete mix where the lowest flexural strength is shown by  $\text{Na}_2\text{SiO}_3$  activated concrete mix (SS4). Almost all AAS concrete shows comparable values of flexural strength with concrete mixes. Among AAS concrete NaOH (SH4) shows higher flexural strength followed by  $\text{Na}_2\text{CO}_3$  activated slag mix (SC4) and then finally the least flexural strength is given by  $\text{NaSiO}_3$  (SS4).

#### G. Punching Shear Test

To find out the Punching Shear Strength a series of tests of micro concrete specimens has been carried out. Three circular

slabs for each three different thickness,  $d''$  were cast, cured, and loaded to failure. The concrete mix ratio of cement: sand: gravel: water (by weight) was 1: 1.34: 2.88: 0.43. The maximum size of the aggregate is 20mm. The sizes of the specimens are 400mm, 200mm and the height of the specimens they have a relation one fourth of the diameter of the specimen. The mix concrete is done by as per IS code provisions and AAS concrete mixtures are done separately in different mixers BS 1881: part 125:1986. The specimens were curing up to 12days. The below graphical figures, show the variation in punching shear for different concrete mixers at particular size cylinder specimen.

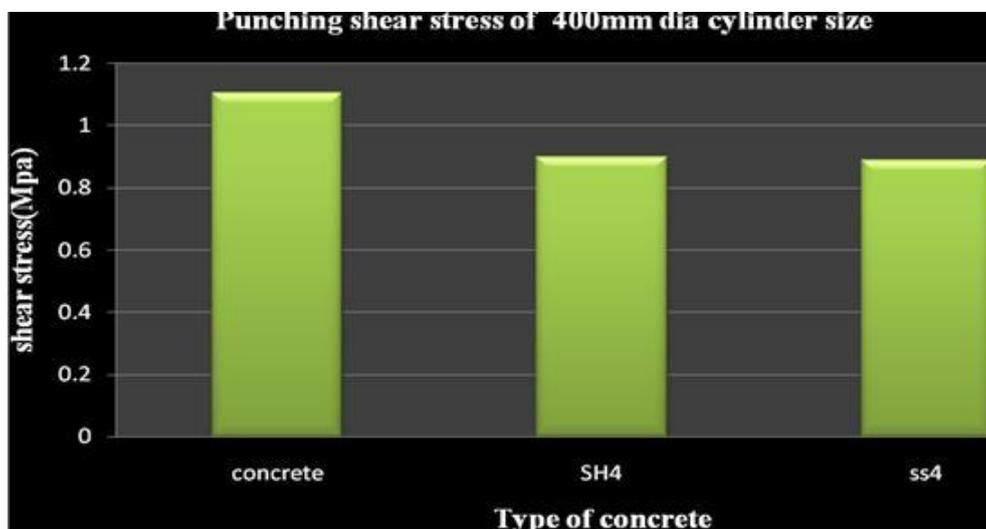

**Figure.5. Punching Shear Stress of 400mm Diameter Cylinder at 12 days curing**

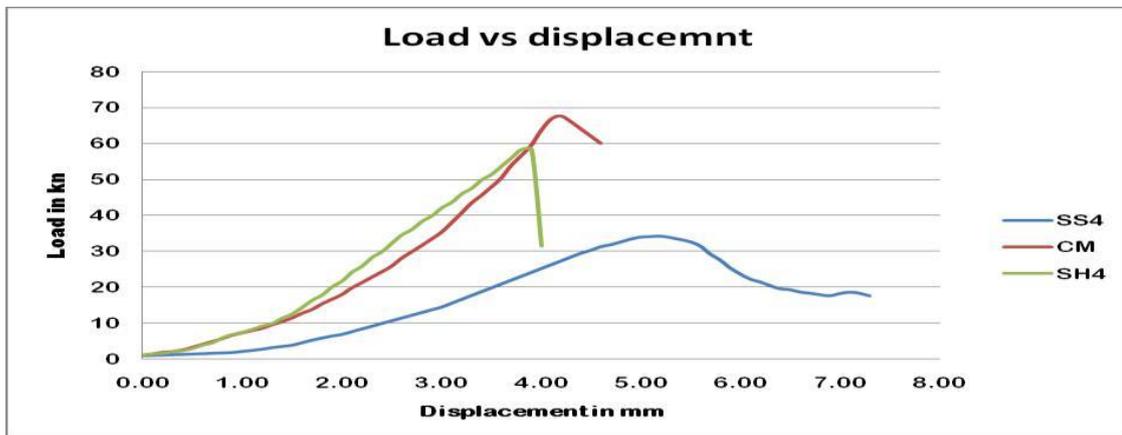


Figure.6. Load Vs Displacement of 400mm Diameter Cylinder

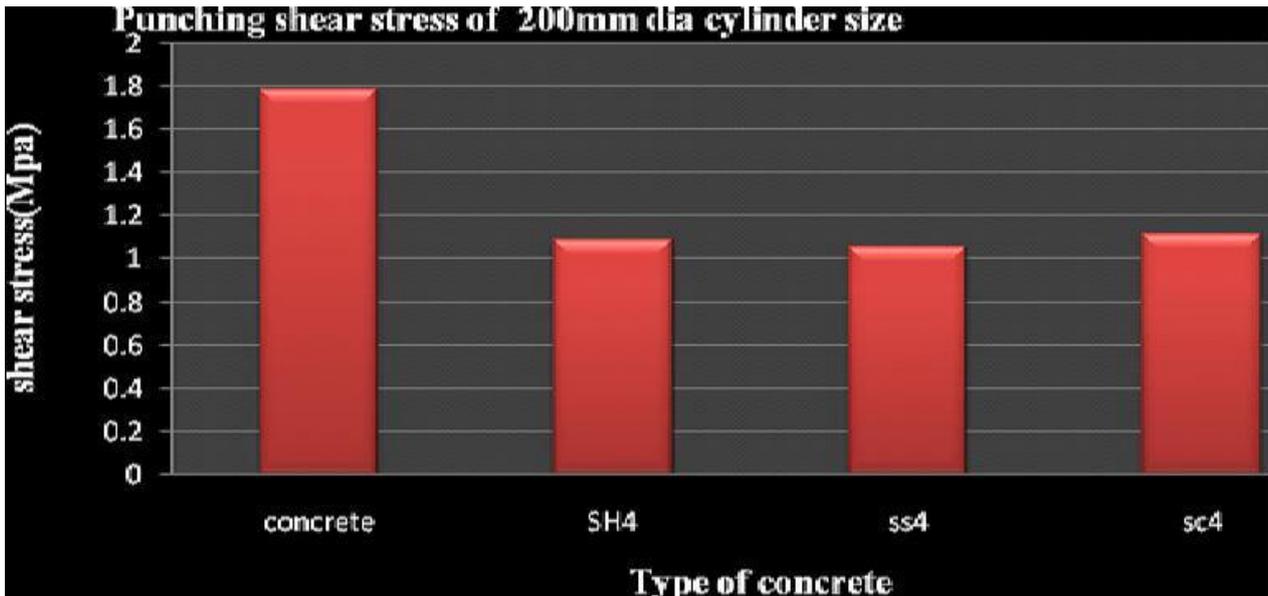


Figure.7. Punching Shear Stress of 200mm Diameter Cylinder at 12 days curing

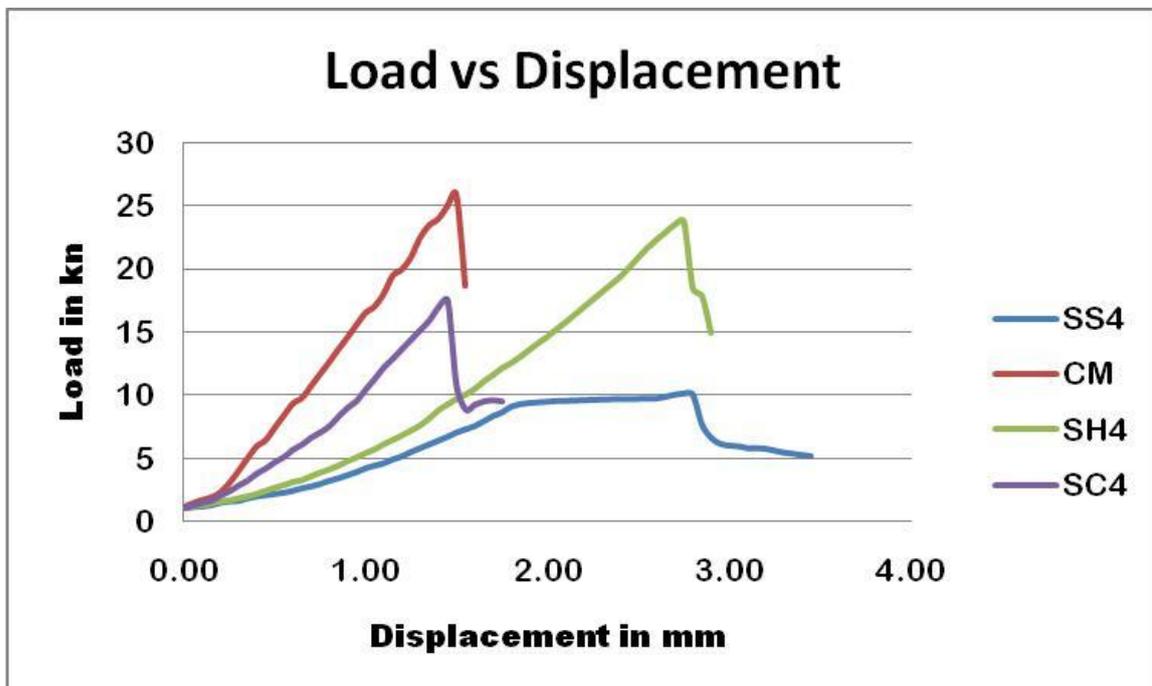


Figure. 8. Load Vs Displacement of 200mm Diameter Cylinder

**H.Results on Punching Shear:** The above figures show the different concrete and different sizes of specimens punching shear stress. In the above graphs the concrete gives the higher

strength when Compare the AAS concrete. The graph show the lower size specimen gives the higher strength when compare to the higher size specimen. All these three AAS concrete NaOH

(SH4) gives the higher strength when compare the  $\text{Na}_2\text{CO}_3$  and  $\text{Na}_2\text{SiO}_3$  gives the very lower value.

## V. CONCLUSION

Overall it can be concluded that AAS concrete has a great potential and presents a viable alternative to OPC to help in decreasing the effect on the environment in terms of energy conservation and less  $\text{CO}_2$  emissions. Sodium silicate activated slag concrete sets rapidly with the higher  $\text{Na}_2\text{O}$  dosage resulting in shorter setting time. The setting time can be prolonged by adding hydrated lime to mix, which increases the final setting time more when compared to initial setting time. Out of all these three activators NaOH is best ;  $\text{Na}_2\text{CO}_3$  was the second;  $\text{Na}_2\text{SiO}_3$  was the third in terms of flexural and punching shear test for the Vizag steel plant slag composition. In compressive test the strength growth rate in early age is high when compared to traditional concrete. From Load vs. displacement curve in flexure test results, the CM mix gives the higher load carrying capacity but less ductility where as SC4 mix shows lower load carrying capacity but very high ductility. Almost all the AAS concrete shows good ductility than traditional concrete. So AAS concrete is good to use where ductile designs are needed i.e., in seismic prone areas. In punching shear test, among all the AAS very less strength compare to all mixes.

## VI. REFERENCES

[1]. Abbas A, Fathifazl G, Isgor OB, Razaqpur AG. Durability of recycled aggregate concrete designed with equivalent mortar volume method. *Cem Concr Comp* (2009).

[2]. Atis CD., Bilim C., Celik O. (2007) "Influence of activator on the strength and drying shrinkage of alkali-activated slag mortar", *Construction and Building Materials*, cited in Elsevier Science Direct.

[3]. Bakharev, T.; Sanjayan, J.G.; Cheng, Y.B. (2001). "Resistance of alkali-activated slag concrete to carbonation", *Cement and Concrete Research*, 31, 1277-1283.

[4]. Basheer, P. A. M. (2001). "Permeation analysis." Handbook of analysis techniques in concrete science and technology, V.S. Ramachandran and J.J. Beaudoin, eds., William Andrew publishing, 985 p.

[5]. Bougara, Lynsdale, Ezziane (2007). "Activation of Algerian slag in mortars", *Construction and Building materials*, cited in Elsevier Science Direct.

[6]. I.S.4031:1988 (part 5) "Determination of initial and final setting time of cement by vicat's apparatus." Indian standards

[7]. Rahal K. Mechanical properties of concrete with recycled coarse aggregate. *Build Environ* 2007.

[8]. Saud, A. O. (2002). "Performance of alkali-activated slag concrete", The University of Sheffield, Sheffield.

[9]. Talling B. and Brandstetr (1989), "present state and future of alkali activated slag concretes", proceedings of the third International Conference on fly ash, silica Fume, slag and natural pozzolans in concrete, Trondheim, SP114-72, 1519-1546.

[10]. Wang S.D., Pu X., Scrivener K.L. and Pratt P.L. (1995). "Alkali activated slag cement and concrete: A review of properties and problems", *Advances in cement research*, (27), 93-102.

[11]. Wang S. D. (1991), "Review of recent research on alkali activated concrete in China", *Magazine of concrete research*, (154), March, 29-35.

[12]. Vladimir Zivica, 2006. "Effects of type and dosage of alkaline activator and temperature on the properties of alkali-activated slag mixtures", *Construction and Building Materials*, cited in Elsevier Science Direct.

[13]. Van Jaarsveld, J.G.S., Van Deventer, J.S.J., and Lukey, G.C. (2002). "The effect of composition and temperature on the properties of flyash-and kaolinite- based geopolymers." *Chemical Engineering Journal*, 89, 63-73.

[14]. Deja, J. and Malolepszy, J., (1989). "Resistance of alkali activated slag mortars to chloride solution." 3<sup>rd</sup> International conference on the use of Fly Ash, Silica Fume, Slag & Natural Pozzolans in concrete, ACI SP-114, Trondheim, Norway, 1547-1561.

[15]. Douglas, E. and Brandstret, J., (1990). "A preliminary study on the alkali activation of granulated blast furnace slag." *Cement and Concrete Research*, 20(5), 746-756.

[16]. Chen, Z. and Liao, X. (1992), "The selection of stimulation agents for alkali-slag cement. 9<sup>th</sup> International Congress on the Chemistry of Cement, New Delhi, India, III, 305-310.

[17]. Gifford P.M. and Gillot J.E. (1996), "Alkali-silica reaction (ASR) and alkali-carbonate reaction (ACR) in activated blast furnace slag cement (ABFSC) concrete", *Cement and Concrete Research*, 26(1), 21-26.

[18]. Kutti, T., Malinowski, R. and Srebnik M., (1982), "Investigation of mechanical properties and structures of alkali activated blast furnace slag mortars." *Silicates industries*, 149-153.

[19]. Glukhovskiy V.D. (1980), "High strength slag alkaline cements", *Proc. 7<sup>th</sup> Int. Congress on the Chemistry of Cement*, Paris.

[20]. Lynsdale, C. J. and sit, W.L. (1992), "The influence of curing on the early age properties of concrete incorporating PFA and slag." *An International Workshop on Blended Cements*, Singapore, 37-42.